

High-frequency conductivity of optically excited charge carriers in hydrogenated nanocrystalline silicon investigated by spectroscopic femtosecond pump–probe reflectivity measurements

He, Wei; Yurkevich, Igor; Zakar, Ammar; Kaplan, Andre

DOI:

[10.1016/j.tsf.2015.03.023](https://doi.org/10.1016/j.tsf.2015.03.023)

License:

Other (please specify with Rights Statement)

Document Version

Peer reviewed version

Citation for published version (Harvard):

He, W, Yurkevich, I, Zakar, A & Kaplan, A 2015, 'High-frequency conductivity of optically excited charge carriers in hydrogenated nanocrystalline silicon investigated by spectroscopic femtosecond pump–probe reflectivity measurements', *Thin Solid Films*. <https://doi.org/10.1016/j.tsf.2015.03.023>

[Link to publication on Research at Birmingham portal](#)

Publisher Rights Statement:

NOTICE: this is the author's version of a work that was accepted for publication in Thin Solid Films. Changes resulting from the publishing process, such as peer review, editing, corrections, structural formatting, and other quality control mechanisms may not be reflected in this document. Changes may have been made to this work since it was submitted for publication. A definitive version was subsequently published in Thin Solid Films, DOI: 10.1016/j.tsf.2015.03.023.

Eligibility for repository checked April 2015

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

Download date: 04. May. 2023

Accepted Manuscript

High-Frequency Conductivity of Optically Excited Charge Carriers in Hydrogenated Nanocrystalline Silicon Investigated by Spectroscopic Femtosecond Pump-Probe Reflectivity Measurements

Wei He, Igor V. Yurkevich, Ammar Zakar, Andrey

PII: S0040-6090(15)00228-X
DOI: doi: [10.1016/j.tsf.2015.03.023](https://doi.org/10.1016/j.tsf.2015.03.023)
Reference: TSF 34180

To appear in: *Thin Solid Films*

Received date: 19 November 2014
Revised date: 6 March 2015
Accepted date: 12 March 2015



Please cite this article as: Wei He, Igor V. Yurkevich, Ammar Zakar, Andrey, High-Frequency Conductivity of Optically Excited Charge Carriers in Hydrogenated Nanocrystalline Silicon Investigated by Spectroscopic Femtosecond Pump-Probe Reflectivity Measurements, *Thin Solid Films* (2015), doi: [10.1016/j.tsf.2015.03.023](https://doi.org/10.1016/j.tsf.2015.03.023)

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

High-Frequency Conductivity of Optically Excited Charge Carriers in Hydrogenated Nanocrystalline Silicon Investigated by Spectroscopic Femtosecond Pump–Probe Reflectivity Measurements

Wei He^a, Igor V. Yurkevich^b, Ammar Zakar^a, Andrey Kaplan^{a,*}

^aUniversity of Birmingham, School of Physics and Astronomy, Birmingham, UK, B15 2TT

^bAston University, Nonlinearity and Complexity Research Group, Birmingham, UK, B4 7ET

Abstract

We report an investigation into the high-frequency conductivity of optically excited charge carriers far from equilibrium with the lattice. The investigated samples consist of hydrogenated nanocrystalline silicon films grown on a thin film of silicon oxide on top of a silicon substrate. For the investigation, we used an optical femtosecond pump–probe setup to measure the reflectance change of a probe beam. The pump beam ranged between 580 and 820 nm, whereas the probe wavelength spanned 770 to 810 nm. The pump fluence was fixed at 0.6 mJ/cm². We show that at a fixed delay time of 300 fs, the conductivity of the excited electron–hole plasma is described well by a classical conductivity model of a hot charge carrier gas found at Maxwell–Boltzmann distribution, while Fermi–Dirac statistics is not suitable. This is corroborated by values retrieved from pump–probe reflectance measurements of the conductivity and its dependence on the excitation wavelength and carrier temperature. The conductivity decreases monotonically as a function of the excitation wavelength, as expected for a nondegenerate charge carrier gas.

Keywords: nanomaterials, high-frequency conductivity, nanosilicon, ultrafast spectroscopy

*Corresponding author

Email address: a.kaplan.1@bham.ac.uk (Andrey Kaplan)

2014 MSC: 00-01, 99-00

1. Introduction

In recent decades, hydrogenated nanocrystalline silicon (nc-Si:H), which is composed of an amorphous silicon phase with embedded nanoclusters of crystalline silicon, has attracted considerable research attention [1, 2]. This material revealed unique electro-optical properties, which have already been investigated for application in photovoltaic solar cells [3], nonvolatile memory devices [4], and thin-film transistors [5]. However, the high-frequency conductivity is not yet well understood or researched, although it the most critical property governing the performance of electro-optical devices. Several critical questions await understanding and explanation: what happens to the charge carriers after they absorb a photon; what is the mechanism of their relaxation and the excess energy release; what physics governs their conductivity. This work tries to address the last question.

In this paper, we report a first attempt to understand the high-frequency conductivity as a function of the pump photon energy. The idea is to establish the dependence of the conductivity immediately (a few hundred femtoseconds) after excitation on the excess energy provided by the photons to the carriers. This short time is sufficient to allow the carrier subsystem to thermalize and settle at a certain thermodynamic distribution characterized by a temperature proportional to the excess energy, but still too short for it to exchange energy with another subsystem of lattice ions.

One of the most advanced tools currently available for the investigation of processes on extremely short timescales is ultrafast optical pump-probe spectroscopy [6]. In brief, the absorption of pump photons with an energy greater than the band gap energy of a semiconductor material generates electron-hole pairs. At sufficiently high concentrations, these charges can be treated as an ambipolar plasma. This free carrier plasma alters the dielectric function of materials and changes the optical response, such as the reflectance, transmittance,

and polarizability [7, 8, 9]. Thus, investigation of the optical response allows
 30 indirect access to the properties of the excited carriers forming the plasma, such
 as the relaxation and recombination times, concentration, carrier temperature,
 and scattering mechanism. The pump-probe reflectance measurement is among
 the most widely used because of its straightforward manageability.

In our investigation, we recorded 25 pump-probe spectra, each of which
 35 corresponds to a pump wavelength between 580 and 820 nm. The reflectance
 is probed by a broadband probe in the range between 765 and 815 nm. The
 results are analyzed using the Drude conductivity and Boltzmann transport
 theories. We show that the thermal distribution of the nascent carriers can be
 described as that of a classical hot nondegenerate gas. The conductivity of the
 40 gas monotonically decreases as the excess energy provided by the pump photons
 decreases.

2. Experimental

2.1. Sample and characterization

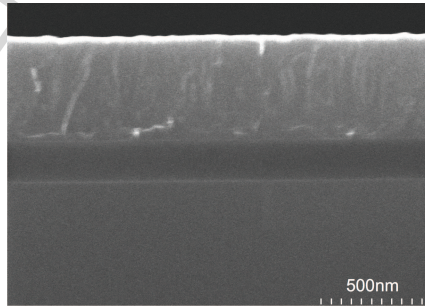


Figure 1: SEM image of cross section of nc-Si:H sample; the top 480 nm-thick layer is nc-Si:H, which was grown on a ~ 188 nm silicon oxide film (SiO_2) on top of a bulk crystalline silicon substrate.

The investigated samples consist of a layer of hydrogenated amorphous silicon (α -Si:H) containing nc-Si grown by a modified plasma deposition technique
 45 similar to that described elsewhere [3, 10]. The dimensions of the sample layers

were estimated using cross-sectional scanning electron microscopy (SEM) images. Figure 1 shows that the top layer of the nc-Si:H film is around 480 nm thick, whereas the underlying silicon oxide film is ~ 188 nm thick. The bottom part of the cross section is a bulk crystalline silicon substrate.

The composition of the nc-Si:H film was investigated by Raman spectroscopy and analysis of the transverse optical modes [11]. In Figure 2(a), the experimental Raman data are shown as black circles. Two Gaussian functions with centers around 520 and 480 cm^{-1} were applied to fit the Raman data. The integrated intensity ratio, $I_{520 \text{ cm}^{-1}} / (I_{520 \text{ cm}^{-1}} + I_{480 \text{ cm}^{-1}})$, can be used to evaluate the crystalline volume fraction in nc-Si:H films [12], where $I_{520 \text{ cm}^{-1}}$ and $I_{480 \text{ cm}^{-1}}$ represent the areas of the respective Gaussians. The fitting results are shown as a red solid line in Figure 2(a). The volume fraction of the silicon crystalline phase estimated using this procedure is around 35%, and the rest is amorphous silicon.

The X-ray diffraction (XRD) data shown in Figure 2(b) were used to estimate the size of the embedded nanoclusters [13, 14, 15]. Using the Scherrer equation [16, 17], we evaluated the mean diameter as $\langle a \rangle \approx 6$ nm. The equation relates the broadening of a peak in a diffraction pattern to the size of the embedded clusters.

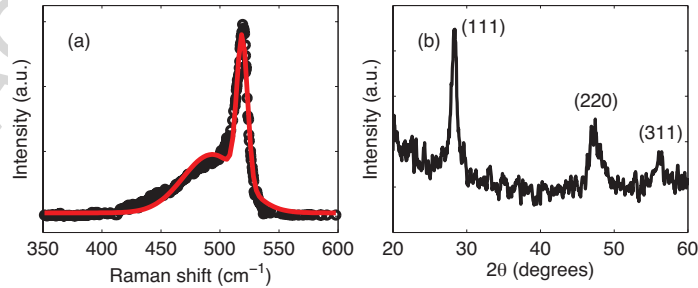


Figure 2: (a) Experimental Raman data (black circles) of the nc-Si:H film. Red line shows a fit with two Gaussians. (b) XRD measurement showing three broadened diffraction peaks: (111), (220), (311).

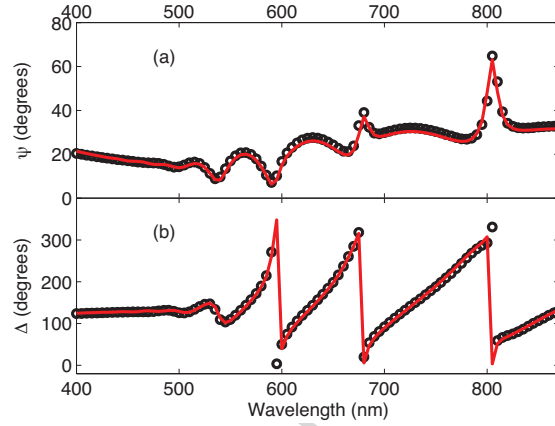


Figure 3: Measured (a) $\psi(\lambda)$ and (b) $\Delta(\lambda)$ (black circles) obtained at an incident angle of 70° . Red solid lines show simulations of multilayer optical model.

2.1.1. Determination of the dielectric function

To obtain the optical properties of the nc-Si:H film, we used a Woollam commercial spectroscopic ellipsometer to measure the polarization state amplitude ratio $\psi(\lambda)$ and the phase difference $\Delta(\lambda)$ at an incident angle of 70° and over a spectral range of 400 to 870 nm. Figure 3 shows the experimental data as black circles. To fit the experimental results and to determine the dielectric function of the top nc-Si film, we used the classical Lorentz model and four-term Forouhi-Bloomer model [18] to express the dispersion relations of the underlying SiO_2 film and crystalline silicon bulk, respectively. To describe the amorphous silicon phase of the nc-Si film, a one-term Forouhi-Bloomer model [19] was applied. Because the nc-Si:H layer consists of an amorphous phase and a crystalline phase, the Bruggeman effective medium approximation was used to express the effective dielectric function [20, 21]. Finally, by using the transfer matrix method [22, 23], the multilayer optical mode was constructed to simulate the ellipsometric response. We also included in the multilayer optical model a thin layer of ~ 10 nm-thick SiO_2 to account for the native oxide on the surface of the top layer. The thicknesses of the layers in the optical model were taken from the SEM cross section measurements. The red solid lines in

Figure 3 show the results of the simulation. The real and imaginary parts of
 85 the effective dielectric function of the nc-Si:H layer, ϵ_{eff}^0 , are shown in Figure 4.
 The obtained dielectric function was used later to analyze the results of the
 pump-probe measurements.

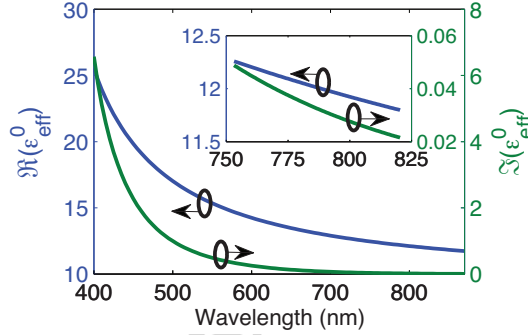


Figure 4: Effective dielectric function of the nc-Si:H layer, $\epsilon_{eff}^0 = \Re(\epsilon_{eff}^0) + i \cdot \Im(\epsilon_{eff}^0)$, obtained from measurements shown in Fig. 3 and simulations of the multilayer optical model. Left and right axes correspond to the real and imaginary parts of the complex dielectric function, respectively. Inset: An enlarged portion of the spectra between 750 and 825 nm.

2.2. Pump-probe setup

An ultrafast laser system (Coherent) was used in the pump-probe setup; it
 90 delivers 1 kHz, 50 fs laser pulses centered around 790 nm. The main beam is
 split into high-intensity pump pulses and low-intensity probe pulses by a pellicle
 beam splitter. Using a light frequency converter (OPA), the pump wavelength
 can be converted to any wavelength between 580 and 820 nm. The pump
 fluence was fixed at 0.6 mJ/cm², and the probe intensity of the fundamental
 95 beam frequency was further attenuated by a neutral density filter. The incident
 angle of the probe beam was set to 70°, whereas the angle of the pump was
 set to around 50°. The polarization of the probe beam was adjusted to provide
 equal contributions of the s- and p-polarization components, and the pump
 beam was always in the s-polarized state. The spatial overlap between the
 100 probe and pump spots on the sample surface was checked by a CCD camera
 equipped with a magnifying lens. The temporal overlap between the probe

and pump pulses was checked by detecting the sum frequency generation on a BBO crystal. By using a computer-controlled retroreflector, the probe delay time with respect to the pump was fixed at 300 fs. Finally, the wavelength of the reflected probe beam was analyzed by a spectrometer (Ocean Optics QE65 Pro), and the collected data are presented here as $\Delta R(\lambda)/R_0$, where R_0 is the reflectance without pumping. Further, $\Delta R = R(t) - R_0$ is the change in reflectance induced by the pump excitation [24, 25], where $R(t)$ is the reflectance measured at a certain delay time (300 fs in this work) by the probe. More details on the pump-probe setup and data modeling are available elsewhere [23, 26, 27]. The 300 fs delay time was chosen because it is sufficiently long for the excited free carrier plasma to build up in the nc-Si:H layer but still short enough to avoid significant population decay [23, 28] and carrier-lattice interactions [29].

3. Experimental Results, Data Analysis, and Discussion

The application of the pump pulse generates a free carrier plasma inside the nc-Si:H layer. These excited carriers change the effective dielectric function of the nc-Si:H layer and the detected intensity of the reflected probe. The excited carrier concentration can generally be derived from the measured intensity change of the reflected probe. The relation between the concentration and the reflectance can be obtained using the classical Drude model [24, 25, 30]. According to the Drude model, the dielectric function of the excited layer after pump excitation, ϵ_{eff} , can be approximated as follows:

$$\epsilon_{eff} = \epsilon_{eff}^0 - \frac{\omega_p^2}{\omega^2 + i \cdot \Gamma \omega} , \quad (1)$$

where ω is the probing frequency. Further, ω_p is the plasma frequency, which is given as $\omega_p^2 = \frac{e^2 N_{eh}}{\epsilon_0 m^* m_e}$, where e , N_{eh} , m^* , and m_e are the electron charge, carrier concentration, optical mass, and free electron mass, respectively. An optical mass of $m^* = 0.17$ was recently estimated for this material [23]. Thus, the excited carrier concentration N_{eh} can be deduced from ω_p . However, there is another important factor affecting the conductivity, that is, the scattering

rate Γ . Thus, the main task is to obtain Γ and N_{eh} for each pump spectrum and establish the high-frequency conductivity according to the relation $\sigma_0 = e^2 N_{eh} / (\Gamma m^* m_e)$. Note that at a relatively short delay time of around 300 fs, carrier-carrier collisions are the main scattering process contributing to Γ . The carrier-phonon collision contribution to the scattering can be neglected, as it is realized on much longer timescales.

Simultaneous experimental determination of Γ and N_{eh} is a complex task that generally requires at least two independent measurements, such as a combination of the transmittance and reflectance [26], or determination of different polarization states of the probe. However, this task can be simplified when Γ has a known dependence on N_{eh} . Here we refer to known models of carrier-carrier scattering published elsewhere [31]. Briefly, these models allow us to calculate the scattering rate as a function of the carrier concentration and carrier temperature as a parameter for the Maxwell-Boltzmann (MB) and Fermi-Dirac (FD) distributions. In this work, we assumed the MB distribution. We note that we independently verified that the FD distribution provides unsatisfactory results. According to the model, the scattering rate can be estimated as follows:

$$\hbar\Gamma = k_B T_{ryd} \left(\frac{T_n}{T} \right)^{3/2} \left(\ln \frac{T^2}{T_n^{3/2} T_{ryd}^{1/2}} \right) M, \quad (2)$$

where k_B is the Boltzmann constant; T_n is the Fermi temperature, which is directly related to the carrier concentration as $k_B T_n = \frac{\hbar^2}{2m^* m_e} (3\pi^2 N_{eh})^{2/3}$; and T_{ryd} and M are the Rydberg temperature and band structure factor, respectively. The band structure factor can be approximated as close to that of bulk silicon [31]. The value of the Rydberg temperature is less well known because of the enhanced carrier-carrier interaction at high carrier concentrations [23]; in our calculation procedure, it was left as an unknown but fixed parameter (that is, it is the same for all pump and probe wavelengths). Finally, for the MB distribution, the temperature of the nascent carriers can be evaluated according to the equipartition theorem, $\frac{3}{2} k_B T = \frac{\hbar\omega_{pump} - E_g}{2}$, where $\hbar\omega_{pump}$ and E_g are the pump photon energy and energy gap of the material, respectively. The latter in our experiment was about 1.2 eV, whereas the former was varied. Thus,

in our fitting procedure we simulate 25 reflectance pump-probe spectra taken at different pump photon frequencies ω_{pump} (corresponding to different carrier temperatures T) for which the carrier concentration N_{eh} is an unknown free parameter, and the Rydberg temperature T_{ryd} is an unknown fixed parameter. The confidence of the simulation procedure is ensured by the small number of fitting parameters and their independence of the probing wavelength in each particular spectrum.

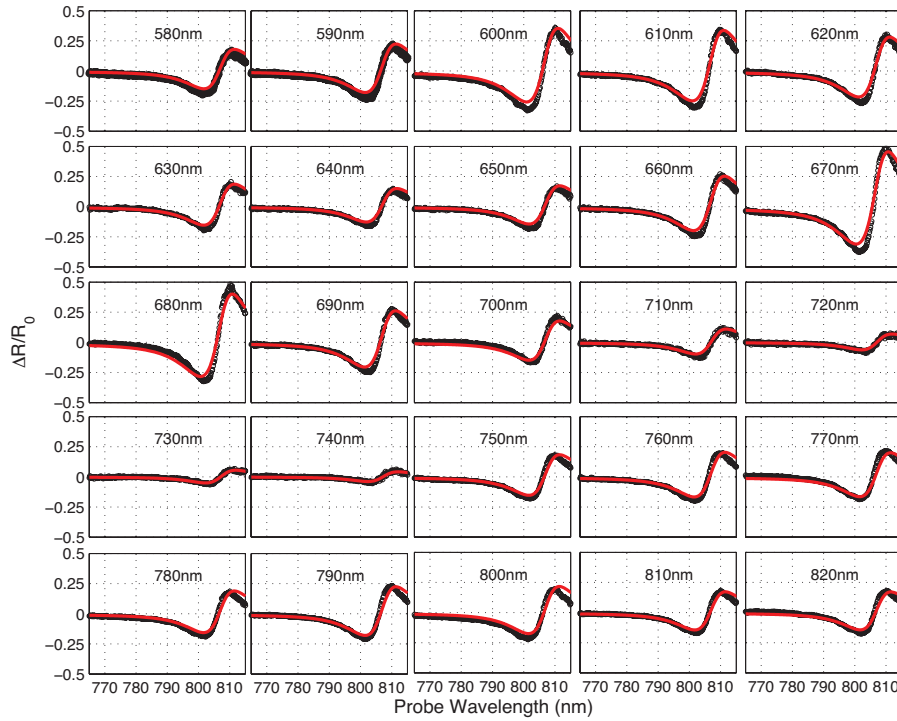


Figure 5: Transient pump-probe experimental data (black dots) for $\Delta R/R_0$ as a function of the probe wavelength taken at different pump wavelengths. Red lines denote simulated results.

Figure 5 shows the pump-probe change in the reflectance data, $\Delta R/R_0$, as a function of the probe wavelength taken at different pump wavelengths. The probe spectrum spans 770 to 810 nm, whereas the pump wavelength covers the region from 580 to 820 nm at 10 nm intervals. All the spectra show a

Fabry–Perot fringe on the red side, similar to that observed elsewhere [23, 30].

170 This fringe originates from the interference effect induced by the change in the dielectric function of the layer following excitation by the pump. However, the contrast of the fringe varies with the pump. This clearly indicates that the excitation efficiency and carrier concentration depend on the pump wavelength for this system. This effect has, however, a simple explanation: The absorbance
175 of the pump pulse depends on the conditions of constructive and destructive interference of the incoming and internally reflected light components within the layer.

Using Eqs. 1 and 2 in the multilayer optical model discussed in previous sections, the data $\Delta R/R_0$ can be fitted to retrieve N_{eh} and Γ as functions
180 of the pump wavelength. The fitting results are shown as red solid lines in Figure 5, which coincide well with the black data points. The retrieved N_{eh} and Γ are shown in Figure 6(a) and (b), respectively. The Rydberg temperature used in the calculation, given by $m_e m^* e^4 / 4\pi \hbar^2 (\epsilon \epsilon_0)^2$, was calculated with the standard constants and optical mass given above, except for ϵ , which is a
185 fixed fitting parameter here. The dielectric constant indicates screening of the carrier–carrier interaction. Unlike the ϵ value for silicon bulk material, which lies between 12 and 13, the value producing the best fit is somewhat lower than 2, demonstrating a tenfold carrier–carrier interaction enhancement, in good
agreement with a previous work [23] (please note that in the previous work the
190 scattering rate estimate provided a higher value because the pumped carriers density was higher). The N_{eh} and Γ retrieved from the simulation show synchronous oscillation as a function of the pump wavelength. The oscillations originate in the constructive and destructive interference of the multiple reflections of the pump beam from the multilayer interfaces.

195 The synchronous behaviour of N_{eh} and Γ is in agreement with a conductivity model of a nondegenerate electron–hole gas in which the scattering rate is proportional to the carrier density. However, N_{eh} and Γ behave differently as a function of the pump wavelength. That is, N_{eh} oscillates around a constant value, whereas Γ tends to increase. This is because N_{eh} depends only on the ab-

sorbance, whereas Γ has an additional dependence on the carrier temperature, which in turn depends on the excess energy provided by the pump photons. According to Eq. 2, a lower temperature (smaller photon energy) causes an increase in the scattering rate..

Finally, with the obtained N_{eh} and Γ values, we calculated the conductivity σ_0 , as shown in Figure 6(c). Remarkably, the conductivity decreases monotonically as a function of the excitation energy. This result indicates that for the MB distribution, the nascent carrier conductivity simply depends on the excess energy (temperature) provided by the pump photons.

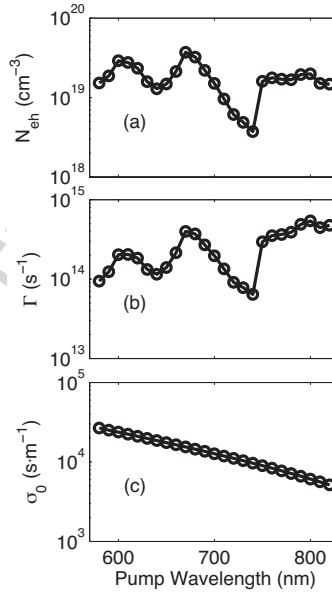


Figure 6: Excited carrier concentration N_{eh} , scattering rate Γ , and conductivity σ_0 as functions of pump center wavelength, obtained using Drude model and MB limitation fitting data $\Delta R/R_0$.

4. Conclusion

In conclusion, in this work we measured and analyzed the pump-probe-wavelength-dependent reflectivity of nc-Si:H samples at a fixed delay time of

300 fs. To establish the optical model of the samples, we investigated their composition with Raman and XRD methods and studied the optical properties using ellipsometry. To find the high-frequency conductivity at this short time, we simulated the pump-probe results using an optical model modified by the Drude contribution of the free carriers excited by the pump. The analysis revealed that the carrier thermodynamic distribution is better described by the classical MB statistics rather than the FD statistics. We found that the conductivity decreases monotonically as the excitation photon energy decreases, as expected for a classical electron-hole plasma. Our work shows that in the design of electro-optical devices one should carefully consider the effect of the balance between the carrier density and the excess energy in order to achieve a desired conductivity.

5. Acknowledgments

The Coherent laser system used in this research was obtained through the Birmingham Science City project: Creating and Characterising Next Generation Advanced Materials, supported by Advantage West Midlands (AWM) and funded in part by the European Regional Development Fund (ERDF). We thank T. Roger, J. Barreto, and D. Chekulaev for help with the experimental setup. We thank J. Bowen for the ellipsometry measurement. We thank EPSRC and DSTL for financial support.

References

- [1] S. Sriraman, S. Agarwal, E. S. Aydil, D. Maroudas, Mechanism of hydrogen-induced crystallization of amorphous silicon, *Nature* 418 (6893) (2002) 62–65.
- [2] A. Shah, P. Torres, R. Tscharnner, N. Wyrsh, H. Keppner, Photovoltaic technology: the case for thin-film solar cells., *Science* 285 (1999) 692.
- [3] A. Shah, J. Meier, E. Vallat-Sauvain, N. Wyrsh, U. Kroll, C. Droz, U. Graf, Material and solar cell research in microcrystalline silicon, *Solar Energy Materials and Solar Cells* 73 (1-4) (2003) 469–491.

- 240 [4] S. Jung, J. Yi, Nanocrystalline-silicon thin-film nonvolatile memory devices
for display applications, *Electron Device Letters, IEEE* 31 (9) (2010) 981–
983.
- [5] C.-H. Lee, A. Sazonov, A. Nathan, J. Robertson, Directly deposited
nanocrystalline silicon thin-film transistors with ultra high mobilities, *Appl.*
245 *Phys. Lett.* 89 (2006) 252.
- [6] A. Othonos, Applied physics reviews applied physics reviews probing ultra-
fast carrier and phonon dynamics in semiconductors, *J. Appl. Phys.* 83 (4)
(1998) 1789.
- [7] C. Shank, R. Yen, C. Hirlimann, Time-resolved reflectivity measurements of
250 femtosecond-optical-pulse-induced phase transitions in silicon, *Phys. Rev.*
Lett. 50 (1983) 454–457.
- [8] A. Sabbah, D. M. Riffe, Femtosecond pump-probe reflectivity study of
silicon carrier dynamics, *Phys. Rev. B* 66 (16) (2002) 165217.
- [9] V. Freilikher, V. I. Tatarskii, M. Pustilnik, I. Yurkevich, Polarization of
255 light scattered from slightly rough dielectric film, *Optics Lett.* 19 (18)
(1994) 1382–1384.
- [10] T. Hamasaki, H. Kurata, M. Hirose, Y. Osaka, Lowtemperature crystal-
lization of doped asih alloys, *Appl. Phys. Lett.* 37 (12) (1980) 1084–1086.
- [11] E. Bustarret, M. Hachicha, M. Brunel, Experimental determination of
260 the nanocrystalline volume fraction in silicon thin films from raman spec-
troscopy, *Appl. Phys. Lett.* 52 (20) (1988) 1675–1677.
- [12] O. Vetterl, F. Finger, R. Carius, P. Hapke, L. Houben, O. Kluth, A. Lam-
bertz, A. Mück, B. Rech, H. Wagner, Intrinsic microcrystalline silicon:
A new material for photovoltaics, *Solar Energy Materials and Solar Cells*
265 62 (1) (2000) 97–108.

- [13] H.P.King, L.E.Alexander, X-ray Diffraction Procedures, Wiley, New York, 1981.
- [14] C. E. Bouldin, E. A. Stern, B. von Roedern, J. Azoulay, Structural study of hydrogenated a-ge using extended x-ray absorption fine structure, Phys. Rev. B 30 (1984) 4462–4469.
- [15] L. Houben, M. Luysberg, P. Hapke, R. Carius, F. Finger, H. Wagner, Structural properties of microcrystalline silicon in the transition from highly crystalline to amorphous growth, Philosophical Magazine A 77 (6) (1998) 1447–1460.
- [16] P. Scherrer, Bestimmung der gröse und der inneren struktur von kolloidteilchen mittels röntgenstrahlen, Nachrichten von der Gesellschaft der Wissenschaften zu Göttingen, mathematisch-physikalische Klasse 1918 (1918) 98–100.
- [17] A. Patterson, The scherrer formula for x-ray particle size determination, Phys. Rev. 56 (10) (1939) 978.
- [18] A. Forouhi, I. Bloomer, Optical properties of crystalline semiconductors and dielectrics, Phys. Rev. B 38 (3) (1988) 1865.
- [19] A. Forouhi, I. Bloomer, Optical dispersion relations for amorphous semiconductors and amorphous dielectrics, Phys. Rev. B 34 (10) (1986) 7018.
- [20] D. Zhang, E. Cherkayev, M. P. Lamoureux, Stieltjes representation of the 3d bruggeman effective medium and padé approximation, Applied Mathematics and Computation 217 (17) (2011) 7092–7107.
- [21] E. Lioudakis, A. Othonos, G. Hadjisavvas, P. Kelires, A. Nassiopoulou, Quantum confinement and interface structure of si nanocrystals of sizes 3–5nm embedded in a-sio₂, Physica E: Low-dimensional Systems and Nanostructures 38 (1) (2007) 128–134.
- [22] E. Hecht, Optics, Pearson Education, 2012.

- [23] T. W. Roger, W. He, I. V. Yurkevich, A. Kaplan, Enhanced carrier-carrier interaction in optically pumped hydrogenated nanocrystalline silicon, Appl. Phys. Lett. 101 (14) (2012) 141904.
- [24] A. Esser, H. Heesel, H. Kurz, C. Wang, G. Parsons, G. Lucovsky, Femtosecond spectroscopic study of ultrafast carrier relaxation in hydrogenated amorphous silicon a-si: H, J. Appl. Phys 73 (3) (1993) 1235–1239.
- [25] K. Sokolowski-Tinten, D. Von der Linde, Generation of dense electron-hole plasmas in silicon, Phys. Rev. B 61 (4) (2000) 2643.
- [26] W. He, I. V. Yurkevich, L. T. Canham, A. Loni, A. Kaplan, Determination of excitation profile and dielectric function spatial nonuniformity in porous silicon by using wkb approach, Opt. Express 22 (22) (2014) 27123–27135.
- [27] A. Kaplan, A. Sajwani, Z. Li, R. Palmer, J. Wilcoxon, Efficient vacuum ultraviolet light frequency downconversion by thin films of cdse quantum dots, Appl. Phys. Lett. 88 (2006) 17105.
- [28] J. Barreto, T. Roger, A. Kaplan, Resolving the ultrafast dynamics of charge carriers in nanocomposites, Appl. Phys. Lett. 100 (24) (2012) 241906.
- [29] H. M. van Driel, Kinetics of high-density plasmas generated in si by 1060- and 530 nm picosecond laser pulses, Phys. Rev. B 35 (15) (1987) 8166–8176.
- [30] M. C. Downer, C. V. Shank, Ultrafast heating of silicon on sapphire by femtosecond optical pulses, Phys. Rev. Lett. 56 (1986) 761–764.
- [31] M. Combescot, R. Combescot, Conductivity relaxation time due to electron-hole collisions in optically excited semiconductors, Phys. Rev. B 35 (1987) 7986–7992.

Highlights

- We study high-frequency conductivity of excited hydrogenated nanocrystalline silicon.
- Reflectance change was measured as a function of pump and probe wavelength.
- Maxwell-Boltzmann transport theory was used to retrieve the conductivity.
- The conductivity decreases monotonically as a function of the pump wavelength.